



MOTIVATION - TO MODEL THE EXPERIMENT

The aim of this work is to supplement the investigation of the corrosion inhibition by the family of organic compounds (viz. 1-actyl-3-methylimidazolium with additional hydrogensulphate, chloride, and bromide) by quantum-chemical calculations, and thus to prepare a framework to predict inhibitor-like properties in designed compounds. To achieve this objective we prepare a realistic model of a single molecule on iron surface Fe(110) by employing the Vienna ab-initio Software Package [1], supplemented with the meta-GGA strongly-constrained and appropriately normed semilocal density functional to model the electronic structure properties of both free and bounded-to-surface molecules of 1-butyl-, 1-hexyl-, and 1-octyl-3-methylimidazolium bromide, chloride, and hydrogensulphate. From our calculations we extract the HOMO/LUMO gap, hardness, electronegativity, and charge transfer of electrons from/to molecules-in-question. It supports the experimental findings and explains the influence of the alkyl chain length and the functional group on the inhibition process.

CHARGE TRANSFER AND OTHER PROPERTIES


We assess the hardness (η) and electronegativity (χ) via the energies of the highest occupied (HOMO) and lowest unoccupied molecular orbitals (LUMO)

$$\eta \equiv \frac{1}{2} (-E_{\text{HOMO}} + E_{\text{LUMO}}),$$

$$\chi \equiv -\frac{1}{2} (E_{\text{HOMO}} + E_{\text{LUMO}}).$$

These quantities, coupled with the Fermi energy (E_F) and the so-called Workfunction (Φ) give first estimation of the charge transfer

$$\Delta N = N_{\text{surface}}^e - N_{\text{free}}^e \approx \frac{\chi_{\text{Fe}} - \chi_{\text{mol}}}{2(\eta_{\text{Fe}} + \eta_{\text{mol}})} \approx \frac{-(E_F - \Phi) - \chi_{\text{mol}}}{2\eta_{\text{mol}}}$$

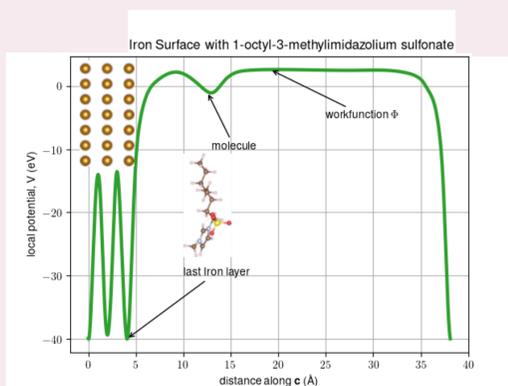


The local potential averaged along the 'vacuum' axis. Note the minima indicating the layers of iron and the molecule, as well as the value in 'infinity' (i.e., Workfunction).

MODELING OF THE INHIBITION OF CORROSION

As the corrosion of iron is driven by it donating the electrons, we expect our inhibitor to accept charge from the surface. For that purpose we calculate the prospective charge transfers: both from the molecule and surface separated (ΔN_{free}) and correlated (ΔN_{correl}). Additionally we perform the Bader charge analysis [4], to calculate the effective charge transfer (ΔN_{Bader}).

As shown both in the Table below and in the Figure on the right, there are three groups of compounds behaving differently in the calculations: (i) pure 1-alkyl-3-methyl-imidazoles; (ii) molecules supplemented by halogens; (iii) molecules supplemented by hydrogen sulphate.

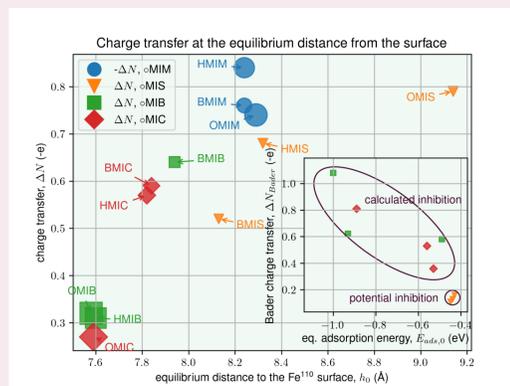

	E_f	E_{HOMO}	E_{LUMO}	η	χ	ΔN_{correl}	ΔN_{free}	ΔN_{Bader}
BMIM	-2.20	-8.40	-4.30	2.05	6.35	0.76	0.68	0.76
HMIM	-2.18	-8.58	-4.46	2.06	6.52	0.84	0.70	0.68
OMIM	-2.18	-8.11	-4.29	1.91	6.20	0.74	0.70	0.66
BMIB	-2.41	-5.55	-1.86	1.84	3.71	-0.64	-0.21	-0.36
HMIB	-2.32	-6.48	-1.75	2.36	4.12	-0.31	-0.22	-0.53
OMIB	-2.29	-6.46	-1.76	2.35	4.11	-0.32	-0.22	-0.81
BMIC	-2.41	-5.70	-1.77	1.97	3.73	-0.59	-0.20	-0.58
HMIC	-2.40	-5.74	-1.77	1.98	3.75	-0.57	-0.22	-0.62
OMIC	-2.30	-6.66	-1.74	2.46	4.20	-0.27	-0.22	-1.08
BMIS	-2.43	-5.87	-1.85	2.01	3.86	-0.52	-0.31	-0.16
HMIS	-2.46	-5.60	-1.81	1.89	3.70	-0.68	-0.32	-0.13
OMIS	-2.49	-5.46	-1.72	1.87	3.59	-0.79	-0.32	-0.11

The Fermi energy, HOMO/LUMO energies, hardness, and electronegativity (all in eV), as well as three types of the calculated charge transfer.

Nevertheless, the analysis of the prospective charge transfer of a correlated system indicates the inhibiting behavior is enhanced-but-not-reached most probably due to the system size.

(i) (marked in yellow) does not accept electron in either of the models. (ii) and (iii) exhibit weak inhibiting properties in the free-molecule model [5] but the Bader charge analysis shows (ii) to be strong acceptors, contrary to (iii).

IRON SURFACE

To model iron surface we minimize the surface energy γ for different slabs, with the area A exposed to vacuum.

	energy (eV/ σ)	A (\AA^2)	γ (eV \AA^{-2})	γ (J m^{-2})
bulk	-8.34069			
Fe(100)	-8.12508	74.132	0.157	2.52
Fe(111)	-7.92548	128.401	0.175	2.80
Fe(110)	-8.04459	69.893	0.153	2.44
W.R. Tyson and W.A. Miller [2]				2.41
I. H. Sahputra <i>et al.</i> [3]				2.44

MOLECULES IN QUESTION

For simplicity we used a four-letter acronym for 1-ALKYL-3-methylimidazolium GROUP molecule


alkyl	formula	symbol	group	formula	symbol
butyl	-C ₄ H ₉	B	-	\emptyset	M
hexyl	-C ₆ H ₁₃	H	Bromide	Br	B
octyl	-C ₈ H ₁₇	O	Chloride	Cl	C
			Hydrogen sulphate	-HSO ₄	S

Hence, 1-octyl-methylimidazolium is being referred as OMIM, whereas 1-butyl-methylimidazolium bromide as BMIB.

IONIZATION

The effective charge on each atom of a 1-butyl-3-methyl-imidazolium. The numbering of carbon and nitrogen atoms corresponds to the schematic figure on the left.

	BMIM	BMIB	BMIC	BMIS
H(BrCl)		-0.8	-0.8	
C(1)	0.3	0.2	0.2	0.2
C(2)	0.7	1.0	1.0	1.1
C(3)	0.4	0.3	0.3	0.3
C(4)	0.4	0.4	0.4	0.3
C(5)	0.4	0.4	0.4	0.5
N(1,3)	-1.3	-1.4	-1.4	-1.4
S				3.9
O			-0.9	-1.4
OH				-0.6

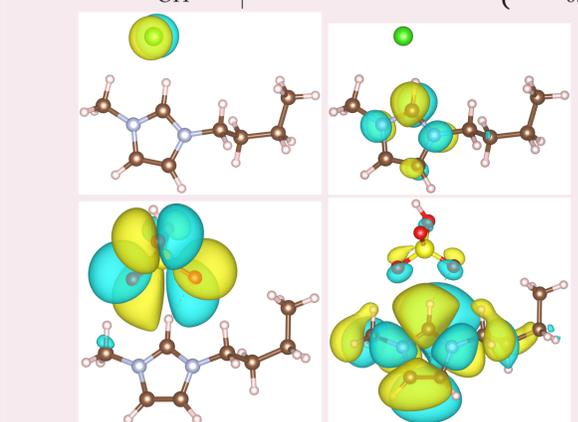

Density plots of the HOMO (left) and LUMO (right) wavefunctions for 1-butyl-3-methyl-imidazolium chloride and 1-butyl-3-methyl-imidazolium hydrogen sulphate.

ACKNOWLEDGMENTS

We would like to thank Dr. Sergiu Arapan and Dr. Pablo Nieves Cordones for their helpful remarks.

This work was supported by the European Regional Development Fund in the IT4Innovations national supercomputing center - path to exascale project, CZ.02.1.01/0.0/0.0/16_013/0001791 within the Operational Programme Research, Development and Education.

See more at www.md-esg.eu.

BIBLIOGRAPHY

- [1] G. Kresse and J. Hafner, Phys. Rev. B **47**, 558 (1993), *ibid.* **49**, 14251 (1994). [3] I. H. Sahputra, *et al.*, Phys. Stat. Sol. (b) **254**, 1600408 (2017).

- [2] W. Tyson and W. Miller, Surface Science **62**, 267 (1977). [4] R. F. W. Bader, Atoms in Molecules - A Quantum The-

ory (Oxford University Press, 1990).

- [5] P. Dohare, *et al.*, Mater. Discov. **9**, 30 (2017).